





OFFICE OF NAVAL RESEARCH

Contract N00014-76-C-0408

Project NR 092-555

Technical Report No. 8

DETACHMENT OF AN ELASTIC MATRIX FROM A RIGID SPHERICAL INCLUSION

by

A. N. Gent



Institute of Polymer Science
The University of Akron
Akron, Ohio 44325

July, 1980

Reproduction in whole or in part is permitted for any purpose of the United States Government

Approved for Public Release; Distribution Unlimited

AE COPY


SECURITY CLASSIFICATION OF THIS PAGE (When Date Entered)	411K-0.
REPORT DOCUMENTATION PAGE	READ INSTRUCTIONS BEFORE COMPLETING FORM
	NO. 3. RECIPIENT'S CATALOG NUMBER
Technical Report 8	14
4. TITLE (and Substitute)	S. TYPE OF REPORT & PENIOD COVER
Detachment of an Elastic Matrix from a	Technical Reported
Rigid Spherical Inclusion	S. PERFORMING ONG. REPORT NUMBER
The state of the s	
7. AUTHOR(a)	S. CONTRACT OR GRANT NUMBERY
10 A. N. /Gent /	NOBB14-76-C-0498
10 A. H. Joene	3 4000
5. PERFORMING ORGANIZATION NAME AND ADDRESS	10. PROGRAM ELEMENT, PROJECT, TA
Institute of Polymer Science/	
The University of Akron Akron, Ohio 44325	NR 092-555
11. CONTROLLING OFFICE NAME AND ADDRESS	12. REPORT DATE
Office of Naval Research	July 1, 1980
Power Program	15. NUMBER OF PAGES (12)
Arlington. Virginia 22217 14. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 14. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 14. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 14. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 15. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 16. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 17. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling Office 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling OFFICE 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling OFFICE 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling OFFICE 18. MONITORING AGENCY NAME & ADDRESS(If different from Controlling OFFICE 18. MONITORING AGENCY NAME & ADDRESS AGENCY NAME & ADDRES	16. SECURITY CLASS (of Misself)
CATIFICA	Unclassified
(11) Jul 80	
	154. DECLASSIFICATION/DOWNGRADIN
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribut	
	ion unlimited.
Approved for public release; distribut	ion unlimited.
Approved for public release; distribut	ion unlimited.
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the obstract entered in Block 20, if different 18. SUPPLEMENTARY HOTES Submitted for publication in: Journal 19. REY WORDS (Continuo en reverse side if necessary and identify by block non	ion unlimited. ***********************************
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the abelrace entered in Block 20, if different 18. Supplementary notes Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse also if necessary and identity by block now Adhesion, Bonding, Elastomers, Fillers	ion unlimited. ***********************************
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the obstract entered in Block 20, if different 18. SUPPLEMENTARY HOTES Submitted for publication in: Journal 19. REY WORDS (Continuo en reverse side if necessary and identify by block non	ion unlimited. ***********************************
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the abelrace entered in Block 20, if different 18. Supplementary notes Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse also if necessary and identity by block now Adhesion, Bonding, Elastomers, Fillers	ion unlimited. ***********************************
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the abelrace entered in Block 20, if different 18. Supplementary notes Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse also if necessary and identity by block now Adhesion, Bonding, Elastomers, Fillers	ion unlimited. ***********************************
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the obstract entered in Block 20, 11 different 18. SUPPLEMENTARY NOTES Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse side 11 necessary and identify by block man Adhesion, Bonding, Elastomers, Fillers Reinforcement 20. APSTRICT (Continue on reverse side 11 necessary and identify by block man An approximate theoretical treat	ion unlimited. of Materials Science bee; , Fracture, Hysteresis, ment is given for detach
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the obstract entered in Block 20, if different 18. SUPPLEMENTARY NOTES Submitted for publication in: Journal 19. REY WORDS (Continue on reverse side if necessary and identify by block non- Adhesion, Bonding, Elastomers, Fillers Reinforcement 20. Agg: RACT (Continue on reverse side if necessary and identify by block non- An approximate theoretical treat ment of an elastomer from a rigid sphe	ion unlimited. of Materials Science bee; Fracture, Hysteresis, ment is given for detach rical inclusion by a
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the obstract entered in Block 20, if different 18. SUPPLEMENTARY HOTES Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse also if necessary and identity by block man Adhesion, Bonding, Elastomers, Fillers Reinforcement 20. APSTRACT (Continue on reverse also if necessary and identity by Neck man An approximate theoretical treat ment of an elastomer from a rigid sphe tensile stress applied to the elastome	ion unlimited. of Materials Science of Materials Science peo) , Fracture, Hysteresis, ment is given for detach rical inclusion by a ric matrix. The inclusi
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the electrons entered in Block 20, if different 18. SUPPLEMENTARY NOTES Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse side if necessary and identify by block man Adhesion, Bonding, Elastomers, Fillers Reinforcement 20. APSTRICT (Continue on reverse side if necessary and identify by block man approximate theoretical treatment of an elastomer from a rigid sphe tensile stress applied to the elastome is assumed to have an initially-debond	ion unlimited. of Materials Science oeo; Fracture, Hysteresis, ment is given for detach rical inclusion by a ric matrix. The inclusi ed patch on its surface
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the obstract entered in Block 20, 11 different 18. SUPPLEMENTARY NOTES Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse side if necessary and identify by block man Adhesion, Bonding, Elastomers, Fillers Reinforcement 20. APSTRACT (Continue on reverse side if necessary and identify by block man approximate theoretical treatment of an elastomer from a rigid sphe tensile stress applied to the elastome is assumed to have an initially-debond and the conditions for growth of the p	ion unlimited. of Materials Science ober) , Fracture, Hysteresis, ment is given for detach rical inclusion by a ric matrix. The inclusied patch on its surface atch are derived from
Approved for public release; distribut 17. DISTRIBUTION STATEMENT (of the electrons entered in Block 20, if different 18. SUPPLEMENTARY NOTES Submitted for publication in: Journal 19. KEY WORDS (Continue on reverse side if necessary and identify by block man Adhesion, Bonding, Elastomers, Fillers Reinforcement 20. APSTRICT (Continue on reverse side if necessary and identify by block man approximate theoretical treatment of an elastomer from a rigid sphe tensile stress applied to the elastome is assumed to have an initially-debond	ion unlimited. of Materials Science of Materials Science over, Fracture, Hysteresis, ment is given for detach rical inclusion by a ric matrix. The inclusi ed patch on its surface atch are derived from trophic debonding is pre

401069

The state of the s

Jab

debond is small. The strain energy dissipated as a result of this detachment, and hence the mechanical hysteresis, are also evaluated. When a reasonable value is adopted for Young's modulus(E) of the elastomeric matrix, it is found that detachment from small inclusions. of less than about 0.1 mm in diameter, will not occur, even when the level of adhesion is relatively Instead, rupture of the matrix near the inclusion becomes the preferred mode of failure at an applied stress given approximately by E/2. For still smaller inclusions, of less than about 1 m in diameter, rupture of the matrix becomes increasingly difficult, due to the increasing importance of a surface energy term. These considerations account for the general features of reinforcement of elastomers. Small-particle fillers become effectively bonded to the matrix, whereas larger inclusions induce fracture near them, or become detached from the matrix, at applied stresses that can be calculated from the particle diameter, the strength of adhesion, and the elasticity of the matrix material.

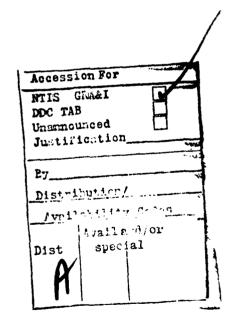

Detachment of an Elastic Matrix from a Rigid Spherical Inclusion

1. Introduction

Elastomers are often filled with high loadings of relatively rigid particulate materials in order to stiffen and strengthen them. These effects depend strongly upon the particle size of the filler and upon the degree of bonding between the elastomer and the filler (1). When the particle size is small, less than about 1 µm, even a moderate degree of interaction between the elastomeric matrix and the filler seems to be sufficient to produce a surprisingly high level of reinforcement. When the particle size is relatively large, the matrix seems to be easily detached from the filler particles at relatively low tensile stresses and the level of reinforcement is correspondingly low (1).

The tensile stress at which an elastic matrix will become detached from a rigid spherical inclusion is derived here on simple theoretical grounds. Only low concentrations of filler are considered, such that the strain fields around each particle do not interact to a significant degree, and the matrix itself is treated as a linearly-elastic material, with Young's modulus <u>E</u>. Detachment is assumed to start at an already-debonded region, present initially on the surface of

the particle. It is assumed to take place by growth of this debonded region when the elastic strain energy thereby released in the matrix is greater than the energy required for further debonding. This is a straightforward application of Griffith's fracture criterion (2). It leads to a prediction of catastrophic debonding when the initially-debonded region is small in size. Moreover, the amount of strain energy lost from the system as a result of debonding can be readily evaluated from the difference between the strain energy levels before and after debonding has taken place. An estimate can be made in this way of the additional mechanical hysteresis due to detachment of the matrix from the filler.

A somewhat similar analysis has recently been put forward, dealing with the conditions for detachment from a spherical
inclusion under a triaxial tension (3). That study differs
from the present analysis in two important respects. The process of detachment was assumed to take place simultaneously at
all points on the spherical surface, rather than progressively
from an initially debonded region. Secondly, the strain energy
released by dilation of the matrix after detachment has taken
place was considered to be wholly expended in the detachment

process itself, in the form of bond fracture energy. In contrast, the analysis developed here, although rather approximate in nature, treats the debonding process as a continuous one, starting from the hypothetical initially-debonded region on the surface of the inclusion. It leads to the prediction of both stable and unstable (i.e., catastrophic) modes of growth of the debond, depending upon the size of the initial debond relative to the size of the inclusion.

In a final section, other modes of failure are considered. It is shown that detachment from small inclusions is improbable, even when the level of adhesion is low and that fracture of the matrix itself in the vicinity of the inclusion becomes increasingly difficult as the size of the inclusion is reduced. These conclusions explain, at least in part, the reinforcing action of small particles.

2. Theoretical considerations

(a) Critical stress for detachment

A single spherical inclusion within an elastic matrix is shown schematically in Figure 1. A small circular area on the surface of the inclusion is assumed to be debonded from the matrix initially. Growth of this debonded patch will take place

when the tensile stress <u>o</u> applied to the specimen at its distant edges reaches a critical value, denoted <u>o</u>. A relation for this critical stress is now derived by means of an approximate energy analysis.

For simplicity, the initially-debonded patch is assumed to be located on the surface of the inclusion in the direction of the applied stress, Figure 1. Other locations would result in higher values of the critical stress, as will be shown later, so that this assumption leads to minimum values for σ_a . The stress field set up in the material is divided conceptually into two regions, as shown in Figure 1: a far-field region where the strain energy density \underline{u} is assumed to be unaffected by the presence of the debonded area, and a region in the immediate vicinity of the debonded zone, shown shaded in Figure 1, within which the strain energy density is assumed to be effectively zero because the debonded zone cannot transmit a tensile stress to the matrix. A similar assumption was made by Rivlin and Thomas in their analysis of an edge crack in a homogeneous elastic solid (4).

The volume ΔV of the unstressed region will be given by $\Delta V = k (r \sin \theta)^3$ (1)

on general dimensional grounds, where $\underline{r}\theta$ is the radius of the circular debonded zone and \underline{k} is a dimensionless quantity evaluated later. The area \underline{A} of the debonded zone is $\underline{2\pi r^2(1-\cos\theta)}$. The loss $\underline{\Delta W}$ in elastic strain energy when the debonded zone increases in area by $\underline{\Delta A}$ is then given by

$$\nabla M = \Omega(\frac{9\theta}{9(\nabla \Lambda)})(\frac{9\theta}{9\theta})\nabla \Psi$$

$$= (3k/4\pi) (Ur \sin 2\theta) \Delta A \qquad (2)$$

In accordance with Griffith's fracture criterion, it is assumed that the debonded area will grow if this reduction in stored strain energy is equal to, or greater than, the energy required for debonding,

namely $G_a \Delta A$, where G_a is the bond fracture energy per unit of bonded surface. The criterion for debonding thus becomes:

$$U \ge 4\pi G_a/3kr \sin 2\theta. \tag{3}$$

In terms of the applied tensile stress $\underline{\sigma}$, \underline{U} is given by $\underline{\sigma^2/2E}$ where \underline{E} is Young's modulus for the composite material. The applied stress $\underline{\sigma}$ necessary to cause debonding is therefore given by

$$\sigma_a^2 = 8\pi G_a E/3kr \sin 2\theta. \tag{4}$$

In order to obtain a value for the numerical quantity k, this result is now specialized to the case when θ is small

and the debonded zone becomes a small circular region of radius $\underline{a} = r\theta$. Mossakovskii and Rybka have treated the corresponding case of the detachment of an elastic half-space from a rigid plate when a circular debond of radius \underline{a} is located at the interface (5). They deduced that

$$\sigma a^2 = 2\pi G_a E/3a. \tag{5}$$

On comparing equations (4) and (5), taking $\underline{\theta}$ to be small, a value of 2 is obtained for the numerical parameter \underline{k} .

It is clear from equation (4) that the tensile stress for detachment is quite—large both when the radius $\underline{r\theta}$ of the initial debond is small, and also when the debonded region is large, when $\underline{\theta} \simeq 90^{\circ}$. It passes through a minimum value when $\underline{\theta} = 45^{\circ}$, i.e., for inclusions which are debonded initially over a substantial fraction of their surface. This minimum value of σ_a is given by

$$\sigma_{a \min}^2 = 4\pi G_a E/3r.$$
 (6)

It is similar in magnitude to the stress causing detachment of an elastic material from a rigid substrate, initiated by a debond of radius \underline{r} , equation (5). It is also similar to that deduced for detachment from a spherical inclusion of radius \underline{r} under a triaxial tension σ_{t} (3),

$$\sigma_t^2 = 8G_aE/3r$$
.

It represents (in the present instance) the lowest stress at which detachment would occur under the most favorable circumstances, i.e., when a relatively large debond is present at the inclusion surface initially, and it is located in a particularly favorable way with respect to the direction of the applied tension. Under all other circumstances the debonding stress will be higher than that given by equation (6). Indeed, when the size of the initial debond, represented by the angle θ , is small, it is clear from equation (4) that debonding will take place in a catastrophic way because the stress required to maintain the debonding process decreases as θ increases. Once the applied stress and stored elastic energy reach their critical levels, then the debond will grow abruptly until $\sin 2\theta$ attains its original value again. If θ is small to start with, then debonding will take place until $\underline{\theta} \simeq 90$, i.e., until debonding is virtually complete.

(b) Energy dissipated in debonding

The loss of stored elastic energy as a result of this abrupt debonding can be evaluated by means of equation (1). The unstressed zone will increase from its small initial size to a final volume of approximately $2r^3$, when \underline{k} is given the

value of 2 deduced earlier. Thus, the decrease in strain energy is approximately $2Ur^3$. If it is assumed, as seems likely, that detachment occurs simultaneously at both poles of the inclusion, then the decrease in strain energy for each inclusion becomes $4Ur^3$. The number n of inclusions per unit volume of the filled material is given by

$$n = 3c/4\pi r^3$$

where \underline{c} is the volume fraction of the composite material occupied by inclusions. Thus, the total reduction in strain energy density caused by debonding is obtained as

$$\Delta U/U_{o} = 3c/\pi, \tag{7}$$

where $\underline{U_0}$ denotes the input strain energy up to the point of detachment. The ratio $\underline{\Delta U/U_0}$, referred to hereafter as the mechanical hysteresis ratio \underline{H} , is therefore predicted to be independent of particle size and proportional to the volume fraction c of particles in the composite.

It should be noted that equation (7) is based upon two special assumptions, which will only hold under quite restricted circumstances. The first is that the stress fields around each particle are assumed not to interact significantly. This implies that the particles are separated by distances comparable to, or greater than, their diameters, and this in turn implies

that their volume fraction <u>c</u> is small, not more than about 10 per cent. The second assumption is that small debonded areas are present initially on the particle surface, and that they are favorably located with respect to the applied stress direction. This implies that there are, in fact, many small debonded areas per particle. Those suitably positioned with respect to the applied stress will presumably act as nuclei for the detachment process.

3. Other modes of failure

The mechanism of detachment treated in the preceding section is likely to be valid only for relatively large particles, weakly bonded to the matrix, and different mechanisms of detachment will operate under other circumstances. For example, when the level of adhesion between the matrix and the inclusion is sufficiently high, the elastomeric matrix will undergo cavitation in the vicinity of the particle (6). In this case, the matrix does not detach from the particle directly, but instead it undergoes internal rupture near the particle surface, nucleated by a small precursor void present within the elastomeric matrix. The void is torn open by triaxial tensions generated in the neighborhood of the particle. The condition for this mode of failure to occur is that the applied tensile stress must reach a critical value, given by (6, 7)

$$\sigma_{\mathfrak{F}} \simeq (E + P) / 2, \tag{8}$$

where \underline{P} denotes the ambient pressure (usually atmospheric pressure and hence small in comparison with \underline{E}).

On comparing the minimum value of the critical stress for detachment, equation (6), with the predictions of equation (8) for the cavitation stress $\sigma_{\mathbf{f}}$, it can be seen that detachment will not take place if

$$G_a / r > 3E/16 \pi$$
 (9)

because the detachment stress $\sigma_{\underline{a}}$ then exceeds the stress $\sigma_{\underline{f}}$ for cavitation. When \underline{E} is given a value of 3 MPa, characteristic of rubbery solids, and $\underline{G}_{\underline{a}}$ a value of 10 J/m^2 , representing a relatively weakly-bonded interface (8), then equation (9) predicts that detachment will not take place for particles having a diameter of less than about 0.1 mm. Instead, the matrix will abruptly tear open near the particle at the applied stress given by equation (8).

Although this failure process is quite different from the detachment mechanism considered earlier, nevertheless the mechanical hysteresis ratio <u>H</u> will still be given by equation (7), to a good approximation, because the assumptions on which that equation was based are still valid. The cavities form abruptly and grow to a size that relieves the high stresses set up in the vicinity of the particle surface in the same way as the abrupt growth of a debond on the particle surface. Indeed, the cavities often tear towards the particle surface as they develop and bring about debonding in this way (6). The initial failure stress, however, is quite different and depends only upon Young's modulus <u>E</u>, equation (8).

If the precursor voids within the elastomeric matrix are even smaller, less than about 100 nm in diameter, then the critical applied stress $\sigma_{\underline{f}}$ will no longer be given by equation (8). Instead, an additional constraint on the expansion of a void becomes significant, arising from its own surface

energy. This additional term, given by $2\gamma/a$ where γ denotes the surface energy of the matrix and \underline{a} denotes the radius of the void, becomes large when the radius \underline{a} is small. Thus, the applied stress must overcome both the elastic resistance to expansion, represented by \underline{E} in equation (8), and a large surface energy contribution as well (9).

that no large precursor voids can be located within the immediate vicinity of a small inclusion. Indeed, it seems reasonable to assume that the largest void that can exist near to an inclusion will be about one order of magnitude smaller in size than the inclusion itself. Thus, cavitation stresses for particles of less than about 1 µm in diameter are likely to be considerably larger than those predicted by equation (8), due to the large surface energy contribution in these cases. Moreover, the smaller the particle, the larger is the stress required to create a cavity in its vicinity by tearing open a precursor void.

It can be concluded that an elastomeric matrix will not detach from small particules, less than about 0.1 mm in size, by debonding, even when the level of adhesion is low. Furthermore, the process of local cavitation in the matrix, leading to the same effects as detachment, will become increasingly difficult as the particle size is further reduced. Rigid inclusions of less than about 1 µm in size are likely to be effectively bonded to the matrix in all circumstances and thus act as reinforcing fillers, in accord with experience (1).

References

- G. Kraus, "Reinforcement of Elastomers by Particulate Fillers," Chap. 8 in "Science and Technology of Rubber," ed. by F. R. Eirich, Adacemic Press, Inc., New York, 1978.
- A. A. Griffith, Philos. Trans. Roy. Soc. (London)
 221, 163-198 (1920).
- 3. D. W. Nicholson, J. Adhesion <u>10</u>, 255-260 (1979).
- 4. R. S. Rivlin and A. G. Thomas, J. Polymer Sci. <u>10</u>, 291-318 (1953).
- V. I. Mossakovskii and M. T. Rybka, P.M.M. <u>28</u>,
 1061-1069 (1964); J. Appl. Math. Mech. <u>28</u>,
 1277-1286 (1964).
- A. E. Oberth, Rubber Chem. Technol. <u>40</u>, 1337-1363
 (1967).
- 7. A. N. Gent and P. B. Lindley, Proc. Roy. Soc. (Lond.) <u>A249</u>, 195-205 (1958).
- 8. A. Ahagon and A. N. Gent, J. Polymer Sci.: Polymer Phys. Ed. 13, 1285-1300 (1975).
- A. N. Gent and D. A. Tompkins, J. Polymer Sci.,
 Part A-2 7,1483-1488 (1969).

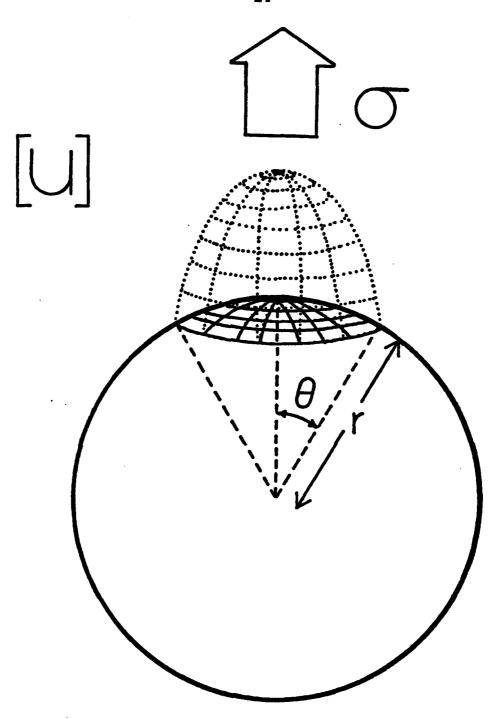


Figure 1. Sketch of a single inclusion showing debonded area and associated volume <u>AV</u> effectively free from stress.

ENERGETIC MATERIALS RESEARCH

DISTRIBUTION LIST

	No. Copies		No. Copies
Assistant Secretary of the Navy (R, E, and S) Attn: Dr. R.E. Reichenbach	1	AFATL Eglin AFB, FL 32542 Attn: Dr. Otto K. Heiney	1 .
Room 5E787 Pentagon Washington, DC 20350		AFRPL Code PACC Edwards AFB, CA 93523	1 .
Office of Naval Research Code 473	10	Attn: Mr. W. C. Andrepont	_
Arlington, VA 22217 Attn: Dr. R. Miller		AFRPL Code CA Edwards AFB, CA 93523	i,
Office of Naval Research Code 2008	1	Attn: Dr. R. R. Weiss	
Arlington, VA 22217 Attn: Dr. J. Enig	•	Code AFRPL MKPA Edwards AFB, CA 93523 Attn: Mr. R. Geisler	1
Office of Naval Research Code 260	1	Code AFRPL MKPA	1
Arlingon, VA 22217 Attn: Mr. D. Siegel	•	Edwards AFB, CA 93523 Attn: Dr. F. Roberto	
Office of Naval Research Western Office 1030 East Green Street Pasadena, CA 91106 Attn: Dr. T. Hall	1 .	AFSC Andrews AFB, Code DLFP Washington, DC 20334 Attn: Mr. Richard Smith	1
Office of Naval Research Eastern Central Regional Office	·2	Air Force Office of Scientific Research Directorate of Chemical & Atmospheric Sciences	1
495 Summer Street Boston, MA 02210 Attn: Dr. L. Peebles		Bolling Air Force Base Washington, DC 20332	
Dr. A. Wood		Air Force Office of Scientific Research	1
Office of Naval Research San Francisco Area Office One Hallidie Plaza Suite 601 San Francisco, CA 94102 Attn: Dr. P. A. Miller	1	Directorate of Aero- space Sciences Bolling Air Force Base Washington, DC 20332 Attn: Dr. L. H. Caveny	
Defense Technical Information Center DTIC-DDA-2 Cameron Station Alexandria, VA 22314	n 12	Anal-Syn Lab Inc. P.O. Box 547 Paoli, PA 19301 Attn: Dr. V. J. Keenan	1

DEF.

	No. Copies		No. Copie
Army Ballistic Research Labs Code DRDAR-BLP Aberdeen Proving Ground, MD 21005	1	Hercules Inc. Eglin AFATL/DLDL Eglin AFB, FL 32542 Attn: Dr. Ronald L. Simmons	1
Attn: Mr. L. A. Watermeier Army Ballistic Research Labs ARRADCOM Code DRDAR-BLP Aberdeen Proving Ground, MD 21005	1	Hercules Inc. Magna Bacchus Works P.O. Box 98 Magna, UT 84044 Attn: Mr. E. H. DeButts	. 1
Attn: Dr. Ingo W. May Army Ballistic Research Labs ARRADCOM Code DRDAR-BLT Aberdeen Proving Ground, MD	1	Hercules Inc. Magna Bacchus Works P.O. Box 98 Magna, UT 84044 Attn: Dr. James H. Thacher	
21005 Attn: Dr. Philip Howe Army Missile Command Code DRSME-RK	2	HQ US Army Material Development Readiness Command Code DRCDE-DW 5011 Eisenhower Avenue Room 8N42	1
Redstone Arsenal, AL 35809 Attn: Dr. R. G. Rhoades Dr. W. W. Wharton		Alexandria, VA 22333 Attn: Mr. S. R. Matos	,
Atlantic Research Corp. 5390 Cherokee Avenue Alexandria, VA 22314 Attn: Dr. C. B. Henderson	t	Johns Hopkins University APL Chemical Propulsion Information Agency Johns Hopkins Road Laurel, MD 20810 Attn: Mr Theodore M. Gilliland	
Ballistic Missile Defense Advanced Technology Center P.O. Box 1500 Huntsville, AL 35807 Attn: Dr. David C. Sayles	1	Lawrence Livermore Laboratory University of California Livermore, CA 94550 Attn: Dr. M. Finger	1
Ballistic Research Laboratory USA ARRADCOM DRDAR-BLP	1	Lawrence Livermore Laboratory University of California Livermore, CA 94550 Attn: Dr. R. McGuire	1
Aberdeen Proving Ground, MD 21005 Attn: ·Dr. A. W. Barrows		Lockheed Missiles and Space Co. P.O. Box 504 Sunnyvale, CA 94088	1
Hercules Inc. Cumberland Aerospace Division Allegany Ballistics Lab P.O. Box 210 Cumberland, MD 21502 Attn: Dr. Rocco Musso	2	Attn: Dr. Jack Linsk Org. 83-10 Bldg. 154	

·	No. Copies	•	No. Co
Lockheed Missile & Space Co. 3251 Hanover Street Palo Alto, CA 94304	1	Naval Research Lab Code 6100 Washington, DC 20375	1
Attn: Dr. H. P. Marshall Dept. 52-35		Naval Sea Systems Command Washington, DC 20362	1
Los Alamos Scientific Lab P.O. Box 1663 Los Alamos, NM 87545 Attn: Dr. R. Rogers, WX-2	1	Attn: Mr. G. Edwards, Code 62R3 Mr. J. Murrin, Code 62R2 Mr. W. Blaine, Code 62R	
Attn: Dr. K. Rugers, WA-2	_	Naval Sea Systems Command	1
Los Alamos Scientific Lab P.O. Box 1663 Los Alamos, NM 87545 Attn: Dr. B. Craig, M Division	1	Washington, DC 20362 Attn: Mr. R. Beauregard SEA 64E	
Naval Air Systems Command Code 330	1	Naval Surface Weapons Center Code R11	1
Washington, DC 20360 Attn: Mr. R. Heitkotter		White Oak, Silver Spring, MD 20910	٠.
Mr. R. Brown		Attn: Dr. H. G. Adolph	
Naval Air Systems Command Code 310	1	Naval Surface Weapons Center Code R13	1
Washington, DC 20360 Attn: Dr. H. Mueller Dr. H. Rosenwasser	•	White Oak, Silver Spring, MD 20910 Attn: Dr. R. Bernecker	
Naval Explosive Ordnance	1	Naval Surface Weapons Center	1
Disposal Facility Indian Head, MD 20640 Attn: Lionel Dickinson	•	Code R10 White Oak, Silver Spring, MD 20910	·
Code D		Attn: Dr. S. J. Jacobs	
Naval Ordnance Station Code 5034	1	Naval Surface Weapons Center Code R11	1
Indian Head, MD 20640 Attn: Mr. S. Mitchell		White Oak, Silver Spring, MD 20910	
	1	Attn: Dr. M. J. Kamlet	
Naval Ordnance Station Code PM4	1	Naval Surface Weapons Center	1
Indian Head, MD 20640 Attn: Mr. C. L. Adams		Code RO4 White Oak, Silver Spring, MD 20910	
Dean of Research	1	Attn: Dr. D. J. Pastine	,
Naval Postgraduate School Monterey, CA 93940 Attn: Dr. William Tolles		Naval Surface Weapons Center Code R13	1
Naval Research Lab	1	White Oak, Silver Spring, MD 20910	
Code 6510 Washington, DC 20375 . Attn: Dr. J. Schnur	-	Attn: Dr. E. Zimet	

	No. Copies	•	No. Copi
Naval Surface Weapons Center Code R101 Indian Head, MD 20640 Attn: Mr. G. L. MacKenzie	1	Navai Weapons Center Code 388 China Lake, CA 93555 Attn: D. R. Derr	1
Naval Surface Weapons Center Code R17 Indian Head, MD 20640 Attn: Dr. H. Haiss	· 1	Naval Weapons Center Code 388 China Lake, CA 93555 Attn: Dr. R. Reed Jr.	1
Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910 Attn: Dr. K. F. Mueller	1	Naval Weapons Center Code 385 China Lake, CA 93555 Attn: Dr. A. Nielsen	1
Naval Surface Weapons Center Code R16 Indian Head, MD 20640 Attn: Dr. T. D. Austin	1	Naval Weapons Center Code 3858 China Lake, CA 93555 Attn: Mr. E. Martin	1
Naval Surface Weapons Center Code R122	1	Naval Weapons Center China Lake, CA 93555 Attn: Mr. R. McCarten	1
White Oak, Silver Spring, MD 20910 Attn: Mr. L. Roslund Naval Surface Weapons Center		Naval Weapons Support Center Code 5042 Crane, Indiana 47522 Attn: Dr. B. Douda	1.
Code R121 White Oak, Silver Spring, MD 20910 Attn: Mr. M. Stosz		Rohm and Haas Company 723-A Arcadia Circle Hunsville, Alabama 35801	1
Naval Weapons Center Code 3853 China Lake, CA 93555 Attn: Dr. R. Atkins		Attn: Dr. H. Shuey Strategic Systems Project Office Dept. of the Navy Room 901	1
Naval Weapons Center Code 3205	1	Washington, DC 20376 Attn: Dr. J. F. Kincaid	
China Lake, CA 93555 Attn: Dr. L. Smith		Strategic Systems Project Office Dept. of the Navy Room 1048	2
Naval Weapons Center Code 3205 China Lake, CA 93555 Attn: Dr. C. Thelen	1	Washington, DC 20376 Attn: Mr. E. L. Throckmorton Mr. R. Kinert	
Naval Weapons Center Code 385 China Lake, CA 93555 Attn: Dr. A. Amster	1	Thiokol Chemical Corp. Brigham City Wasatch Division Brigham City, UT 84302 Attn: Dr. G. Thompson	1 ·

<u>N</u>	o. Copies	No.	Copies
USA ARRADCOM DRDAR-LCE Dover, NJ 07801 Attn: Dr. R. F. Walker	1	Georgia Institute of Technology Office of Research Administration Atlanta, Georgia 30332 Attn: Professor Edward Price	1
USA ARRADCOM DRDAR-LCE Dover, NJ 07801 Attn: Dr. N. Slagg	1	Univ. of Utah Dept. of Mech. & Industrial Engine MEB 3008 Salt Lake City, Utah 84112 Attn: Dr. Stephen Swanson	1 ering
U.S. Army Research Office Chemistry Division P.O. Box 12211 Research Triangle Park, NC 27709	1	Space Sciences, Inc. 135 Maple Avenue Monrovia, CA 91016 Attn: Dr. M. Farber	1
Institute of Polymer Science University of Akron Akron, OH 44325 Attn: Professor Alan N. Gent		Washington State University Dept. of Physics Pullman, WA 99163 Attn: Professor G.D. Duvall	1
SRI International 333 Ravenswood Avenue Menlo Park, CA 94025 Attn: Dr. Y.M. Gupta	1	Univ. of Maryland Department of Mechanical Eng. College Park, MD 20742 Attn: Professor R.W. Armstrong	ī
Graduate Aeronautical Lab. California Institute of Technolo Pasadena, CA 91125 Attn: Professor W.G. Knauss	• .	The Catholic University of America Physics Department 520 Michigan Ave., N.E. Washington, D.C. 20017 Attn: Professor T. Litovitz	1
Pennsylvania State University Dept. of Mechanical Engineering University Park, PA 16802 Attn: Professor Kenneth Kuo Office of Naval Research	1	Sandia Laboratories Division 2513 P.O. Box 5800 Albuquerque, N.M. 87185 Attn: Dr. S. Sheffield	1
800 N. Quincy St. Arlington, VA 22217 Attn: Dr. G. Neece Code 472 Thiokol Corp. Huntsville		IBM Research Lab. K42.282 San Jose, CA 95193 Attn: Dr. Thor L. Smith	1
Huntsville Div. Huntsville, AL 35807 Attn: Mr. J.D. Byrd	•	California Institute of Tech. Dept. of Chemical Engineering Pasadena, CA 91125 Attn: Professor N.W. Tschoegl	1
Washington State University Dept. of Physics Pullman, WA 99163 Attn: Prof. T. Dickinson		Northwestern University Dept. of Civil Engineering Evanston, IL 60201 Attn: Professor J.D. Achenbach	1
University of California Dept. of Chemistry 405 Hilgard Avenue Los Angeles, CA 90024		Office of Naval Research Structural Mechanics Program Arlington, VA 22217	1
	<i>t-</i>		· ""

DEF.

	No. Copies
University of California Berkeley, CA 94720 Attn: Prof. A.G. Evans	1
Texas A&M Univ. Dept. of Civil Engineering College Station, TX 77843 Attn: Professor Richard A. Sch	l napery
SRI International 333 Ravenswood Ave. Menlo Park, CA 94025 Attn: Mr. M. Hill	1
Los Alamos Scientific Laborator Los Alamos, NM 87545 Attn: Dr. J.M. Walsh	ry 1

